

DOI 10.31489/2020No1/73-76

UDC29.19.04, 29.19.21

TIME-RESOLVED LUMINESCENCE EXCITED WITH N₂ LASER OF YAG:CE CERAMICS FORMED BY ELECTRON BEAM ASSISTED SYNTHESIS

Karipbayev Zh.^{1,2}, Alpyssova G.^{1*}, Mussakhanov D.², Lisitsyn V.², Kukenova A.¹, Tulegenova A.³

¹L.N. Gumilyov Eurasian National University, Nur-Sultan, Kazakhstan, gulnur-0909@mail.ru

²National Research Tomsk Polytechnic University, Tomsk, Russia

³al-Farabi Kazakh National University, Almaty, Kazakhstan

In this paper, an attempt to synthesize the phosphor using powerful hard radiation fluxes. White light-emitting diodes (LEDs) are considered a good lighting devices due to their unsurpassed qualities, such as energy saving and long service life. The synthesized ceramics has the characteristic properties of YAG: Ce, YAGG: Ce phosphors. In total, 10 types of phosphors were chosen for research. Phosphors differed in the presence of Ce₂O₃ and gadolinium ions incorporated as a modifier.

Keywords: white LEDs, yttrium-aluminum garnet, phosphor, ceramics, synthesis in the radiation field.

Introduction

On YAG:Ce based phosphors are the most promising for use in LEDs [1-2]. Phosphors are crystalline multicomponent systems [3-4]. The synthesis of YAG:Ce phosphors is carried out by different methods: solid-state reactions, [5], laser ablation [6], sol-gel method [7], hydrothermal [8], pyrolytic spraying [3], coprecipitation [9], using combustion [10] and others. The most common is the synthesis using solid-phase reactions. But this method, as well as the others listed, requires to use a high temperatures. The melting points of the components are from 2455 °C in Y₂O₃ to 2075 °C in Al₂O₃. Therefore, the reproducibility of the synthesis results is low: the elemental composition of microcrystals differs significantly from that included in the mixture, the composition of different batches of phosphor even during synthesis under the same conditions, and the same initial composition of the mixture are changes [11-13]. This also affects to the luminescent properties of phosphors. Therefore, work is constantly ongoing to improve synthesis technologies. In this work, we present the results of studies YAG:Ce based phosphors synthesized in a radiation field.

1. Experimental technique

The samples were synthesized by high-power electron beam generated electron accelerator ELV-6. The possibility of using such a method was first demonstrated in [13-14]. Synthesis in the radiation field should obviously contribute to the occurrence of solid-phase reactions. In the present work, phosphors of different compositions were synthesized with a Y₂O₃ charge content of 22 to 36 wt%, Al₂O₃ ~56 to 62 wt%, Ce₂O₃ ~4.8 to 9.1 wt%, and Gd₂O₃ ~0 to 12 wt% (Table 1).

The structure and elemental composition of these samples were described in [15]. The luminescence spectra of samples and the luminescence excitation spectra were measured using an Cary Eclipse (Agilent) fluorescence spectrophotometer. The photoluminescence kinetics was registered by a Hamamatsu PMT through a monochromator when excited by a nitrogen laser at a wavelength of 337 nm.

Table 1. The initial composition of the synthesized samples

No.	Compositions	Sample number
1	Al ₂ O ₃ (59.5%) + Y ₂ O ₃ (35.7%)+ Ce ₂ O ₃ (4.8%)	1
2	Al ₂ O ₃ (56.8%) + Y ₂ O ₃ (34.1%)+ Ce ₂ O ₃ (9.1%)	2
3	Al ₂ O ₃ (59.5%) + Y ₂ O ₃ (23.8%) + Gd ₂ O ₃ (11.9%) + Ce ₂ O ₃ (4.8%)	3
4	Al ₂ O ₃ (56.8%) + Y ₂ O ₃ (22.7%)+ Gd ₂ O ₃ (11.4%) + Ce ₂ O ₃ (9.1%)	4
5	Al ₂ O ₃ (56.8%) + Y ₂ O ₃ (34.1%)+ Ce ₂ O ₃ (9.1%)	5
6	Al ₂ O ₃ (59.5%) + Y ₂ O ₃ (23.8%)+ Gd ₂ O ₃ (11.9%) + Ce ₂ O ₃ (4.8%)	6
7	Al ₂ O ₃ (59.5%) + Y ₂ O ₃ (35.7%)+ Ce ₂ O ₃ (4.8%)	7
8	Al ₂ O ₃ (56.8%) + Y ₂ O ₃ (34.1%)+ Ce ₂ O ₃ (9.1%)	8
9	Al ₂ O ₃ (56.8%) + Y ₂ O ₃ (22.7%)+ Gd ₂ O ₃ (11.4%) + Ce ₂ O ₃ (9.1%)	9

2. Results and Discussion

The synthesized samples were ceramic balls with a diameter of 3-6 mm of a characteristic yellow color. The samples were crushed into powder, photoluminescence spectra were measured upon excitation by laser radiation λ 337 nm. Excitation spectra and decay kinetics were also measured. It was established that the main luminescent characteristics of the synthesized ceramic samples are mainly similar to those known for the solid-phase synthesis of phosphors obtained by traditional methods [16]. Fig. 1 shows the results of study the luminescence spectra of powdered samples of different compositions; the luminescence spectra have the form of a monopole by exciting on 337 nm.

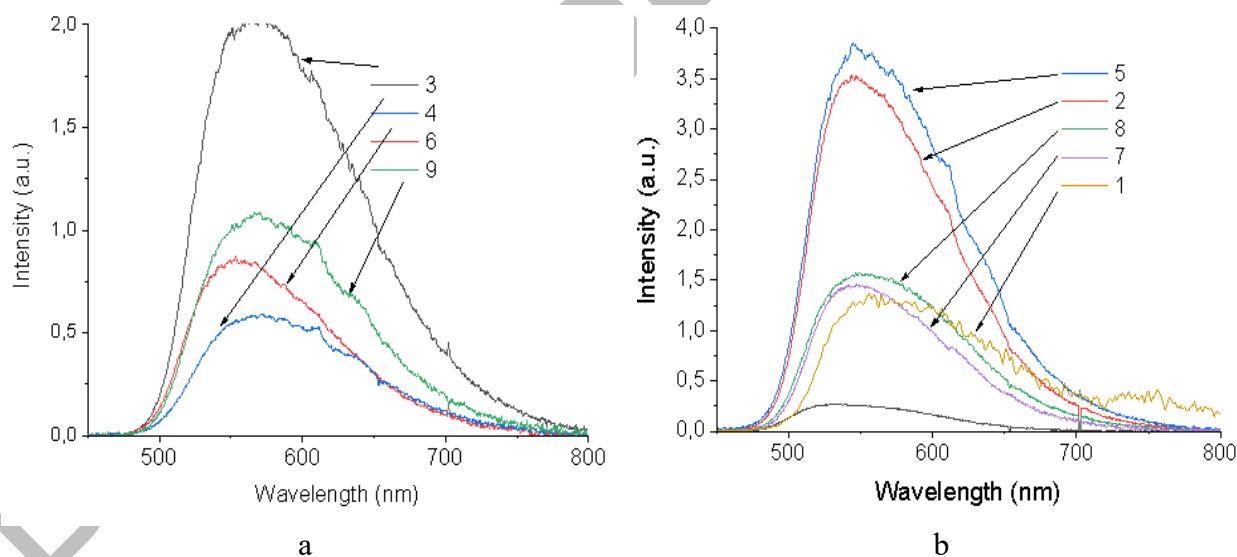


Fig. 1. Luminescence spectrum of YAG (a) and YAGG (b) ceramics samples excited by 337 nm.

A comparison of results of measuring the characteristics of the spectra gives the following. There is a large variation in the positions and half-widths of the luminescence bands. In YAG:Ce ceramic samples the positions of bands are in the range from 546 to 563 nm, the half-width is from 0.42 to 0.49 eV. In YAGG:Ce from 548 to 570 nm and from 0.44 to 0.48 eV, respectively. In general, tendency is: the entering of gadolinium leads to a band shift to the red region. The wide variation in the band characteristics is explained by the following. In strongly defective systems, which are YAG:Ce ceramics samples, the luminescence center is an element of a nanod defect, a complex defect [17]. Nanod defect is formed during the synthesis. The formation does not have time

to complete at a high rate of ceramic synthesis. Therefore, small differences in the synthesis conditions, primarily during the preparation of mixtures, can lead to deviations in the structure of the nanodefekt. This is manifested in a change in the characteristics of the spectrum due to differences in environment of luminescence center. The maxima position, the half-width of the spectra, the kinetic parameters at a wavelength of registration of 540 nm pulsed photoluminescence are presented in table 2.

Table 2. The maxima position, the half-width of the spectra, the kinetic parameters at a wavelength of registration of 540 nm

Sample number	$\lambda_{\text{ex}}=337$ nm		Photoluminescence kinetics parameters at $\lambda = 540$ nm			
	ΔE , eV	λ_{max}	τ_1 , ns	A_1	τ_2 , ns	A_2
1	0.494371	563	38.78	0.51	70	0.6
2	0.427453	545			62.34	
3	0.477145	570	28	0.5	64.29	0.6
4	0.459989	548	21.44	0.85	60	0.37
5	0.441487	546			65	
6	0.441029	554	29	0.4	62	0.69
7	0.422713	548			67.71	
8	0.456703	550			70	
9	0.484883	570	37.16	0.475	68.37	0.6

Figure 2 (a,b) shows the results of study of the luminescence decay kinetics of synthesized ceramic samples after excitation by a nanosecond laser measurement pulse at 337 nm.

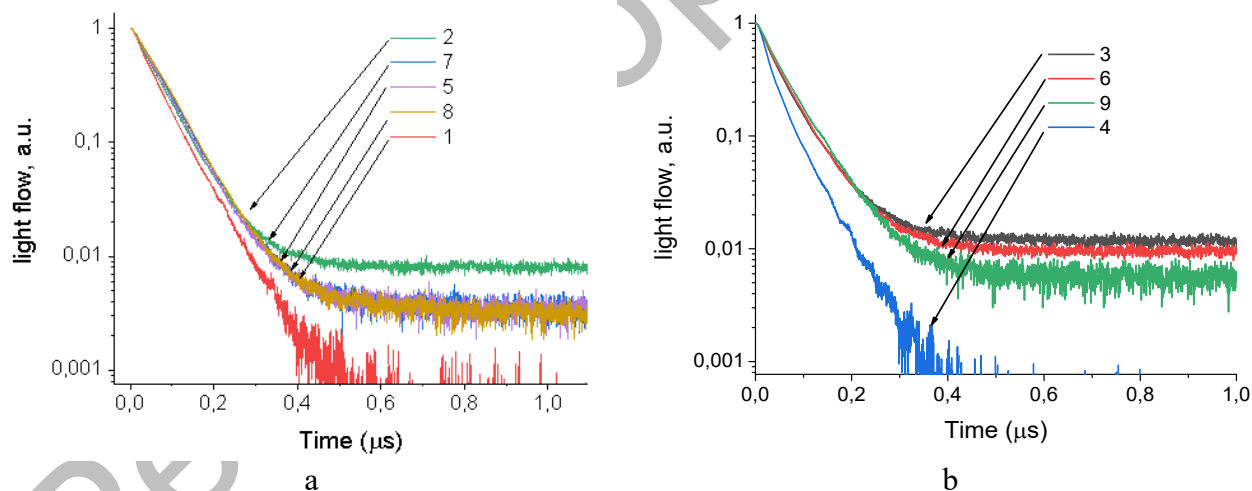


Fig. 2. Photoluminescence kinetics of YAG ceramics excited by a 337 nm nitrogen laser

In the majority of studied ceramic samples, at least two stages of decay with characteristic times \sim ns and long in the microsecond range take place. For some samples, the decay pattern is described by a single exponent. There is a difference in the decay amplitude ratios in the first stage

Conclusion

The luminescent characteristics of YAG: Ce ceramic samples synthesized in a radiation field were studied. In general terms, the spectral and kinetic characteristics of ceramics luminescence are similar to those known for YAG: Ce phosphors and ceramics obtained using the solid-state reaction method. Therefore, the radiation method for the synthesis of luminescent ceramics which differ

fundamentally from the existing one, can be considered as an alternative. It was shown that the luminescence characteristics of the synthesized samples have a large variation. This is explained in the framework of the notion that the luminescence center, cerium ion, are elements of nanodefects which formed during the synthesis. In the synthesis of samples, the radiation field, which takes 1 s, does not complete the formation of nanodefects. Subsequent annealing of the samples is required to complete their formation.

Acknowledgments

The work was carried out within the framework of the grant AP08052050 of the Ministry of Education and Science of the Republic of Kazakhstan. This research was supported by Tomsk Polytechnic University CE Program.

REFERENCES

- 1 Zehua Liu, Shuxing Li, et al. Composite ceramic with high saturation input powder in solid-state laser lighting. *Ceramics International*, 2018, Vol.44, pp. 20232–20238.
- 2 Țucureanu V., Munteanu D. Enhanced optical properties of YAG:Ce yellow phosphor by modification with gold nanoparticles. *Ceramics International*, 2019, Vol. 45, pp.7641-7648.
- 3 Barbaran J.H., Ghamsari M.S., Javaheri I., et al. Growth and spectral properties of Ce³⁺:YAG single crystal. *Journal of optoelectronics and advanced materials*, 2018. Vol. 20, pp. 431 – 434.
- 4 Murai S., Fujita K., Iwata K., Tanaka K. Scattering-based hole burning in Y₃Al₅O₁₂:Ce³⁺ monoliths with hierarchical porous structures prepared via the sol-gel route. *J. Phys. Chem.: C*, 2011, Vol. 115, No.36, pp. 17676–17681.
- 5 Hakuta Y., Haganuma T., Sue K., et al. Continuous production of phosphor YAG: Tb nanoparticles by hydrothermal synthesis in supercritical water. *Materials Research Bulletin*, 2003, Vol. 38, pp. 1257-1265.
- 6 He G., Mei L., Wang L., Liu G., Li J. Synthesis and luminescence properties of nano-/microstructured Y₃Al₅O₁₂:Ce³⁺ microspheres by controlled glass crystallization. *Cryst. Growth. Des.*, 2011, Vol. 11, pp.5355–5361.
- 7 Karbowski M., Kepinski L., et al. Structural and luminescent properties of nano-sized NaGdF₄:Eu³⁺ synthesised by wet-chemistry route. *Journal of Alloys and Compounds*, 2004, Vol. 380, pp. 315 – 320.
- 8 Huczko A. Fast combustion synthesis and characterization of YAG:Ce³⁺ garnet nanopowders. *Phys. Status Solidi B*, 2013, Vol. 250, No.12, pp. 2702–2708.
- 9 Xianqiang Chen, et.al. Highly transparent ZrO₂-doped (Ce,Gd)₃Al₃ Ga₂O₁₂ ceramics prepared via oxygen sintering. *Journal of the European Ceramic Society*, 2015, Vol. 35, pp. 3879-3883.
- 10 Dantelle G., Salaiin M., Bruyere R., et al. Luminescent coatings prepared from optimized YAG:Ce nanoparticles. *Thin Solid Films*, 2013, Vol. 543, pp. 36-42.
- 11 Lisitsyn V.M., Lisitsyna L., Dauletbekova A., et al. Luminescence of the tungsten-activated MgF₂ ceramics synthesized under the electron beam. *Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms*, 2018, Vol. 435, pp. 263-267.
- 12 Lisitsyn V.M., Golkovskii M.G., Lisitsyna L., et al. MgF₂-Based Luminescing Ceramics. *Russian Physics Journal*, 2019, Vol. 61, Issue 10, pp. 1908–1913.
- 13 Lisitsyn V.M., Golkovskii M.G., Musakhanov D.A., et al. YAG based phosphors, synthesized in a field of radiation. *Journal of Physics: Conference Series*, Vol. 1115, Issue 5, pp.052007.
- 14 Musakhanov D.A., Tulegenova A.T., Lisitsyn V.M., et al. Structural and luminescent characteristics of YAG phosphors synthesized in the radiation field. *IOP Conf. Series: Materials Science and Engineering*, 2019. Vol. 510, pp. 012031.
- 15 Nie, Lijun Xu, Mingfu Zhang Microstructures, optical properties and application in WLEDs of large- size YAG:Ce³⁺-Al₂O₃eutectic grown by HDS method. *Journal of Alloys and Compounds*, 2019, Vol. 782, pp. 348-354.
- 16 Wagner A., Ratzker B., Kalabukhov S., et.al. Residual porosity and optical properties of spark plasma sintered transparent polycrystalline cerium -doped YAG. *Journal of the European Ceramic Society*, 2019, Vol. 39, pp. 1436-1442.
- 17 Alpysova G., Mussakhanov D., Karipbayev Zh, et.al. Luminescence spectra of YAG:Ce phosphors synthesized in a field of radiation. *HTRA-2019 IOP Conf. Series: Materials Science and Engineering*, 2020, Vol. 754, pp. 012014.