



Manganite Synthesis By Different Methods

MUKHAMETKALI MUSAGALIEVICH MATAEV¹, SIDDHARTH (MONTU) SAXENA²,
GENNADY SEMENOVICH PATRIN³, ZHANAR YLIASOVNA TURSINOVA^{1*},
ASSEL TAUPYKOVNA KEZDIKBAYEVA⁴, MARZHAN ABDYZHAPAROVNA
NURBEKOVA¹ and GAUKHAR UMIRALIEVNA BAITASHEVA¹

¹Kazakh state women's teacher training university, 050000, Aiteke bi, 99, Almaty, Kazakhstan.

²University of Cambridge, Madinley Road, Cambridge, CB3 0HE, United Kingdom.

³Siberian Federal University, Svobodny pr. 79, Krasnoyarsk, Russia.

⁴The Karaganda State University of the name of academician E.A.Buketov,
Universitetskaya 28, Karaganda, Kazakhstan.

*Corresponding author E-mail: zhanar.tursin@mail.ru

<http://dx.doi.org/10.13005/ojc/340315>

(Received: January 30, 2018; Accepted: February 28, 2018)

ABSTRACT

Nanostructural dysprosium manganite doped with bismuth, synthesized by three methods: solid-phase, sol-gel and citrate-nitrate. The composition of the synthesized powders was compared to determine the optimal technique. Using X-ray diffraction, the influence of annealing conditions on the structure of manganite was studied. The result of XRD showed that manganite, synthesized variants of methods has orthorhombic structure.

Keywords: Dysprosium orthomanganite, Sol-gel combustion, Citrate-nitrate combustion, structure, X-ray.

INTRODUCTION

Preparation of materials in the form of various sediments¹⁻³ is referred to the family of the wet synthesis procedures known from a number of advantages compared with traditional high temperature solid state processing methods, such as excellent control of stoichiometry of the final powders with the possibility to obtain uniformity and

mixing in atomic scale, the distribution of narrow particles, minor contamination of the product during the homogenization of the source connections, low energy consumption, low aging time and simple equipment⁴.

Research described in⁵, showed that the crystalline structure is a sequential process; the crystalline product is obtained at temperature of



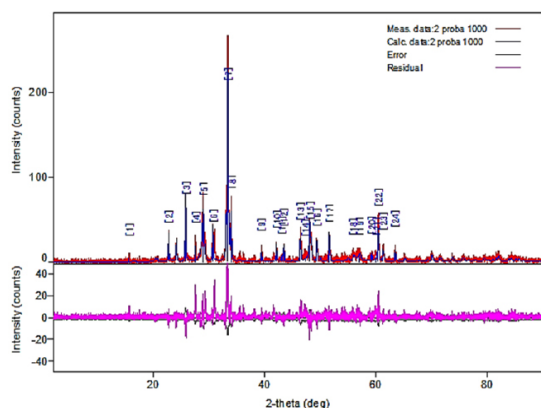


Fig. 2. The diffraction pattern of the manganite synthesized by the sol-gel method

Citrate-nitrate method

Perovskite type of BDMO was received by the citrate-nitrate method using as source oxides Dy_2O_3 (b.p.), Bi_2O_3 (b.p.), Mn_2O_3 (b.p.). Same as in the second method, the mixture of oxides was dissolved in distilled water. 2M nitric acid as a precipitating agent was added to the obtained solution. Citric acid in the ratio of the oxides 1:2 was used as the reaction medium. Chelating effect is favorable for pH value. Thus an adequate volume of 2M of solution HNO_3 were added to increase the pH value of the mixtures up to 7. The obtained mixture was evaporated using an electrical plate at 80 °C and continuous stirring to remove the excess solvent before formation of the dry semi-product and annealed at 500 °C for 10 h to obtain the desired powder.

The presence of the source oxide in the mixture is maintained at a temperature of 700-800 °C. At this with increasing temperature the manganese is rapidly recovered, being in a sample composition in the form of a mixture of oxides with different degree of oxidation. The bismuth oxide is finally included in the structure of solid solution based on dysprosium manganite at 800-900 °C, the dysprosium oxide remains in the form of oxide or hydroxide up to 900 °C, and then reacts. Final heat treatment of the precursors was performed in a muffle furnace at different temperatures (900, 1000 °C) for 21 h, in a muffle furnace. Formation of the new phase is completed at a temperature of 1000 °C.

In Fig. 3, the peaks marked in blue indicate peaks before improvement of the phase and the

peaks marked with pink are the remaining after the refinement of the phase by the Rietveld method.

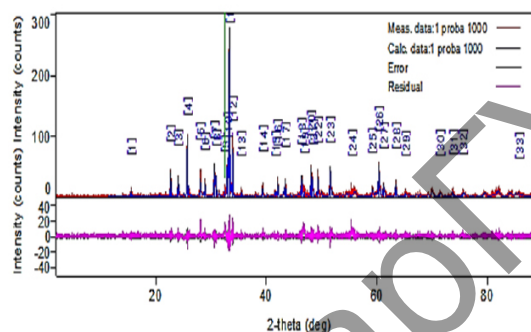


Fig. 3. The diffraction pattern of the manganite synthesized by citrate-nitrate method

RESULTS AND DISCUSSION

The formation of new phases was controlled by the method of x-ray phase analysis produced by X-ray diffractometer Miniflex 600 (Rigaku) using $CuK\alpha$ radiation filtered by the Ni filter ($U = 30$ kV, $J = 10$ MA, the rotation speed of 1000 pulses per second, time constant = 5 sec., the range of angles 2θ from 5 to 90). Radiographs of the synthesized polycrystalline powders were indicated by the homology method (homologue is a distorted structure type of perovskite). The density of manganites were determined by the pycnometric method according to GOST 2211-65. Toluene served as indifferent liquid. The density of the manganite was measured 4 – 5 times and data were averaged.

The results of the synthesized manganite radiograph indexing by different methods show that the manganites have the orthorhombic structure with the following unit cell parameters (Table 2).

The reliability of the indexing results is controlled by a satisfactory coincidence of experimental and calculated values of the inverse squares of the interplanar spacing's ($104/d^2$), and the coincidence degree of the x-ray and pycnometric densities values of the studied compounds.

Thus, the double bismuth– manganite BDMO was synthesized by various methods. Using the ceramic technology, considering the Tamman's conditions, the authors defined temperature regime of the synthesis of the dual mixed manganite BDMO. The type of crystal system and unit cell parameters

were determined by the radiographic method. It is established that a complex mixed manganite is crystallized in the orthorhombic crystal system; the correctness of the results of x-ray studies of the manganite is confirmed by the good concordance between the experimental and calculated values ($104/d_2$), concordance between the values of x-ray

and pycnometer densities. The comparative analysis of parameters between the lattice parameters of the source $\delta\text{-Bi}_2\text{O}_3$ shows that the values of the parameters «a» and «b» satisfactorily coincide with the lattice parameters $\delta\text{-Bi}_2\text{O}_3$, the parameter «c» is distorted from the value of the «a» parameter on $\sqrt{2}$.

Table 1: The results on indexing of radiographs of manganites synthesized with different methods

No	[°2Th.]	d[Å]	Int. [%]	$10^4/d^2_{\text{exp}}$	hkl	$10^4/d^2_{\text{theor}}$
Solid-phase method						
1	22.55(4)	4.31421	2	537.27	(1,0,1)	538.31
2	23.94(7)	3.91843	10	651.29	(1,1,0)	653.52
3	25.62(3)	3.73505	12	716.81	(0,0,2)	718.83
4	33.247(19)	3.47001	30	830.49	(1,1,1)	833.52
5	41.78(10)	2.91993	10	1172.88	(0,2,0)	1173.89
6	46.17(7)	2.71955	30	1352.09	(0,2,1)	1354.15
7	48.07(5)	2.70358	100	1368.11	(1,1,2)	1370.16
8	51.53(3)	2.64232	30	1432.28	(2,0,0)	1435.3
9	60.30(12)	2.55575	0	1530.95	(1,2,0)	1532.01
Sol-gel method						
1	11.38	7.769	0.2	165.67	(1,1,0)	165.67
2	16.12	5.494	1.8	331.3	(2,0,0)	331.3
3	19.78	4.486	6.5	496.91	(2,1,1)	496.91
4	22.87	3.885	2.7	662.54	(2,2,0)	662.54
5	25.62	3.474	2.2	828.59	(0,1,3)	828.59
6	28.11	3.172	100	993.88	(2,2,2)	993.88
7	30.42	2.936	3	1160.08	(1,2,3)	1160.08
8	32.57	2.747	37	1325.2	(4,0,0)	1325.2
9	34.61	2.59	3.9	1490.74	(4,1,1)	1490.74
10	36.54	2.457	1.7	1656.49	(0,2,4)	1656.49
11	38.4	2.342	2.3	1823.16	(3,3,2)	1823.16
12	40.18	2.243	0.6	1987.65	(4,2,2)	1987.65
Citrate-nitrate method						
1	15.57	5.688	32.9	309.09	(0,0,1)	309.09
2	15.95	5.55	0.6	324.65	(1,1,0)	324.65
3	20.75	4.278	1.5	546.41	(0,2,0)	546.41
4	22.36	3.972	1.5	633.84	(1,1,1)	633.84
5	24.1	3.69	9.7	734.42	(1,2,0)	734.42
6	24.39	3.647	10	751.85	(2,0,0)	751.85
7	26.04	3.419	12.7	855.46	(0,2,1)	855.46
8	26.55	3.355	9.9	888.41	(2,1,0)	888.41
9	28.82	3.095	68	1043.95	(1,2,1)	1043.95
10	29.06	3.07	8.5	1061.02	(2,0,1)	1061.02
11	30.92	2.89	100	1197.3	(2,1,1)	1197.3
12	31.43	2.844	14.5	1236.35	(0,0,2)	1236.35
13	32.23	2.775	6.8	1317.52	(2,2,0)	1317.52
14	33.72	2.656	41.2	1417.57	(1,3,0)	1417.57
15	35.44	2.531	27.2	1561.05	(1,1,2)	1561.05

Table 2: The unit cell parameters of the manganite obtained by different methods

No	Obtaining method	a	b	c	Vun.cell., Å ³	Z	P _{X-ray} g/cm ³	P _{pyc.} g/cm ³
1	Solid-state reaction	5.294	5.839	7.410	229	4	7.648	7.651
2	Sol-gel method	5.2793	5.83	7.382	227.26	4	7.765	7.761
3	Citrate-nitrate method	5.832	5.278	7.386	227.38	4	7.758	7.76

CONCLUSION

BDMO manganite nanoparticles were synthesized in three ways. When using a solid-phase method multiphase manganite has been received. The use of sol-gel and citrate-nitrate methods made it possible to obtain single-phase crystalline nanoparticles in comparison with the solid-phase method. The solid-phase synthesis method is

not optimal for obtaining dysprosium-bismuth manganite.

ACKNOWLEDGMENT

This article was prepared with the financial support of the grant of the Ministry of Education and Science of the Republic of Kazakhstan No 05130165 "Development and physical basis of new crystal systems in the class of multiferroics".

REFERENCES

1. Yener, D. O.; Giesche, H. *J. Am. Cer. Soc.*, **2001**, *84*(9), 1987-1995.
2. Natarajan, U.; Handique, K.; Mehra, A.; Bellare, J. R.; Khilar, K.C. *Langmuir.*, **2003**, *2*, 2670 – 2678.
3. Uskokovic, V.; Drogenik, M. *Mat. Sci. Forum.*, **2004**, *453*(4), 225 – 230.
4. Uskokovic, V.; Drogenik, M. *J. Magn. Magn. Mat.*, **2006**, *303*, 214 – 220.
5. Mataev, M. M.; Saxena, S. M.; Tursinova, Zh. I.; Nurbekova, M. A.; Sarsenbaeva, Z. B.; Seitbek, A. *Zh. Chem. J. Kazakhstan.*, **2017**, *4*, 181-188.